


## Sintered Neodymium-Iron-Boron Magnets

These are also referred to as "Neo" or NdFeB magnets. They offer a combination of high magnetic output at moderate cost. Please contact Arnold for additional grade information and recommendations for protective coating. Assemblies using these magnets can also be provided.

Characteristic	Units	Magnetic Properties		
		min.	nominal	max.
<b>Br</b> , Residual Induction	Gauss	12,900	13,100	13,400
	mT	1290	1310	1340
<b>H<sub>cB</sub></b> , Coercivity	Oersteds	12,200	12,500	12,800
	kA/m	971	995	1019
<b>H<sub>cJ</sub></b> , Intrinsic Coercivity	Oersteds	30,000		
	kA/m	2,388		
<b>BH<sub>max</sub></b> , Maximum Energy Product	MGOe	40	43	45
	kJ/m <sup>3</sup>	318	338	358

Characteristic	Units	Thermal Properties	
		C //	C ⊥
Reversible Temperature Coefficients <sup>(1)</sup>			
	of Induction, α(Br)	%/°C	-0.12
	of Coercivity, α(H <sub>cj</sub> )	%/°C	-0.47
Coefficient of Thermal Expansion <sup>(2)</sup>	ΔL/L per °Cx10 <sup>-6</sup>	7	-1
Thermal Conductivity	kcal/mhr°C	5.3	5.8
Specific Heat <sup>(3)</sup>	cal/g°C	0.11	
Curie Temperature, T <sub>c</sub>	°C	310	
Flexural Strength	psi	41,300	
	MPa	285	
Density	g/cm <sup>3</sup>	7.6	
Hardness, Vickers	Hv	620	
Electrical Resistivity, ρ	μΩ • cm	150 // 130 ⊥	

Notes: (1) Coefficients measured between 20 and 200 °C  
 (2) Between 20 and 200 °C. Values are typical and can vary.  
 (3) Between 20 and 140 °C

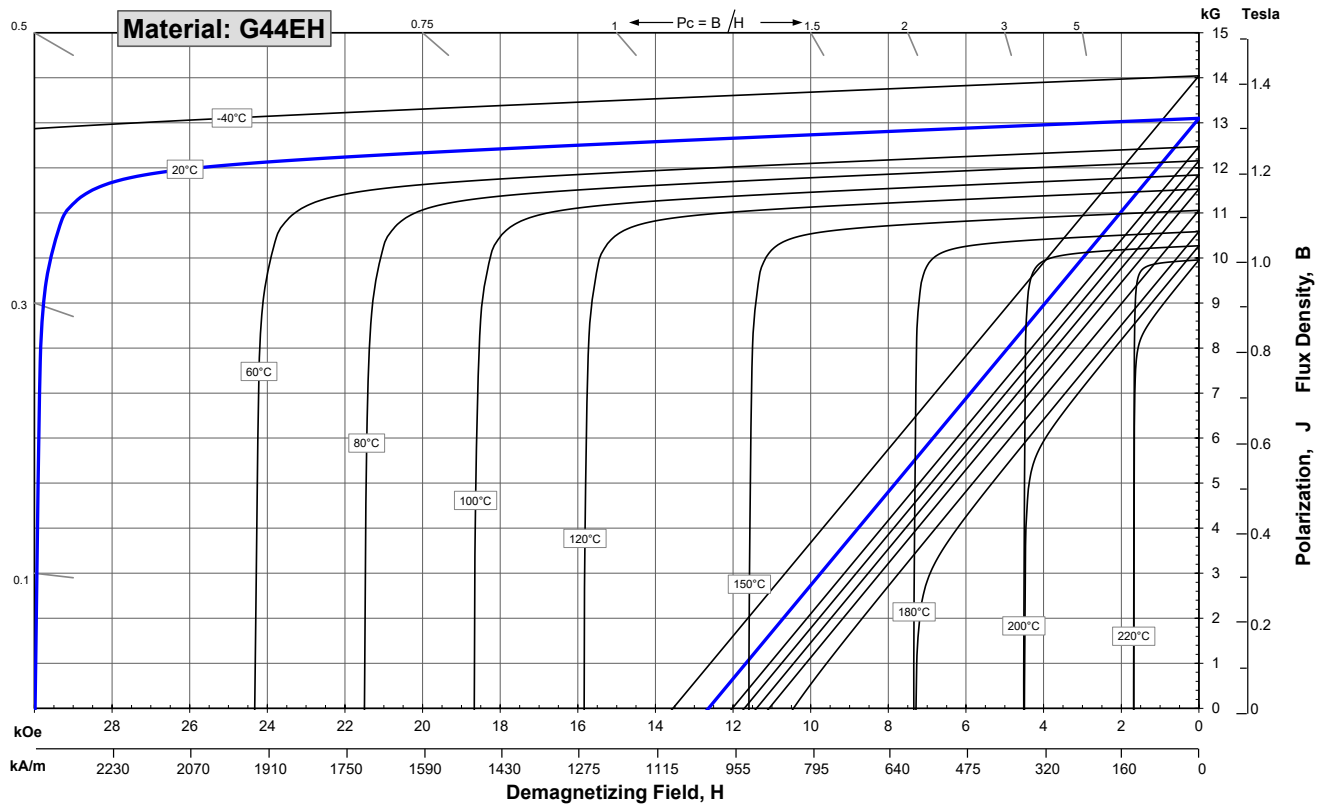

1 kA/m = 12.566 Oe 1 kOe = 79.577 kA/m

**Notes** The material data and demagnetization curves shown above represent typical properties that may vary due to product shape and size. **Demagnetization curves show nominal Br and minimum H<sub>cj</sub>.** Magnets can be supplied thermally stabilized or magnetically calibrated to customer specifications. Additional grades are available. Please contact the factory for information.